

## Evolution of the Spectral Function in Mott-Hubbard Systems with $d^1$ Configuration

A. Fujimori, I. Hase, H. Namatame, Y. Fujishima, and Y. Tokura  
*Department of Physics, University of Tokyo, Bunkyo-ku, Tokyo 113, Japan*

H. Eisaki and S. Uchida  
*Department of Applied Physics, University of Tokyo, Bunkyo-ku, Tokyo 113, Japan*

K. Takegahara  
*Department of Physics, Tohoku University, Sendai 980, Japan*

F. M. F. de Groot  
*Research Institute for Materials, University of Nijmegen, Toernooiveld, 6525 ED Nijmegen, The Netherlands*  
 (Received 18 February 1992)

We have studied the photoemission spectra of perovskite-type  $Ti^{3+}$  and  $V^{4+}$  oxides, which have formally the  $d^1$  configuration ranging from a Mott insulator to a paramagnetic metal. The results indicate that as the Mott-Hubbard gap closes, spectral weight is transferred from the upper and lower Hubbard bands to the region near the Fermi level with decreasing  $U/W$  ( $U$ ,  $d$ - $d$  Coulomb repulsion energy;  $W$ , one-electron  $d$ -band width), i.e., from the incoherent to the coherent part of the single-particle spectral function.

PACS numbers: 71.28.+d, 78.70.Dm, 79.60.-i

Electron correlation in narrow-band systems has been extensively studied using the Hubbard model [1], in which the magnitudes of the on-site Coulomb energy  $U$  and the one-electron band width  $W$  control the properties of the system: With an integral number of electrons per atomic site, the system is metallic when  $U/W < 1$  and becomes insulating when  $U/W > 1$ . The single-particle spectral function  $\rho(\omega)$ , i.e., the imaginary part of the single-particle Green's function  $G(\omega)$ , characterizes physical properties of many-electron systems and can be measured by photoemission and inverse-photoemission spectroscopy. No clear picture for the  $\rho(\omega)$  of the Hubbard model, however, has been obtained so far, particularly on the metallic side of the Mott transition. The complication originates from the nature of the splitting between the lower and upper Hubbard bands, which is fundamentally different from the splitting of one-electron energy bands [2].

In this Letter, we have studied the photoemission spectra of various Mott-Hubbard-type  $3d$  transition-metal oxides which cover a certain range of  $U/W$  values on both sides of the Mott transition. We compare materials with the same  $d$ -band filling, namely,  $Ti^{3+}$  and  $V^{4+}$  compounds having formally the  $d^1$  configuration, since the lowest energy required for the charge fluctuation  $d^n + d^n \rightarrow d^{n+1} + d^{n-1}$  ( $=U_{\text{eff}}$ ) depends on the multiplet structures of the  $d^n$ ,  $d^{n+1}$ , and  $d^{n-1}$  configurations. As a result of the degeneracy of the Ti or V  $3d$  ( $t_{2g}$ ) orbitals,  $U_{\text{eff}} \sim u' - j$ , where  $u'$  is the Coulomb energy between two electrons in different  $t_{2g}$  orbitals and  $j$  is the corresponding exchange integral. Then the Mott transition occurs at  $(u' - j)/W \sim 1$ , where  $W$  is now the width of the  $t_{2g}$  band.

We have studied  $YTiO_3$  (a ferromagnetic insulator [3]),  $LaTiO_3$  (a "barely metallic" antiferromagnet with

weak ferromagnetism below  $T_C \sim 125$  K [3-5]), and  $SrVO_3$  (a paramagnetic metal [6]). They have a cubic ( $SrVO_3$ ) or distorted ( $LaTiO_3$ ,  $YTiO_3$ ) perovskite structure (GdFeO<sub>3</sub>-type structure); the Ti-O-Ti or V-O-V bond angle is distorted from the ideal value of  $180^\circ$  to  $\sim 155^\circ$  in  $LaTiO_3$  and  $\sim 140^\circ$  in  $YTiO_3$  [7]. The distortion reduces the overlap between neighboring  $d$  orbitals and hence  $W$  in the order  $SrVO_3 \rightarrow LaTiO_3 \rightarrow YTiO_3$ . In addition, in going from  $Ti^{3+}$  to  $V^{4+}$  oxides, the metal  $d$  level is lowered relative to the oxygen  $p$  level due to the increase in the valence and atomic number of the transition-metal ion, which would increase the  $p$ - $d$  hybridization and hence increase  $W$  and decrease  $U_{\text{eff}}$ . Thus,  $U_{\text{eff}}/W$  decreases in the order  $YTiO_3 \rightarrow LaTiO_3 \rightarrow SrVO_3$ .

Polycrystalline samples were made by a melt-quenching technique, and were characterized by thermogravimetry analysis ( $SrVO_{2.99 \pm 0.01}$ ,  $LaTiO_{3.03 \pm 0.01}$ , and  $YTiO_{3 \pm 0.14}$ ), x-ray diffraction, dc conductivity, and magnetic susceptibility measurements. Photoemission experiments were performed using a spectrometer equipped with a He discharge lamp ( $h\nu = 21.2$  and  $40.8$  eV) and a Mg x-ray source and also using synchrotron radiation at beamline BL-2 of the Synchrotron Radiation Laboratory (Institute for Solid State Physics, University of Tokyo) and at BL-11D of the Photon Factory (National Laboratory for High Energy Physics). The samples were cleaned *in situ* by scraping with a diamond file. In order to avoid the degradation of the surfaces in an ultrahigh vacuum, the samples were cooled down to  $\sim 80$  K using liquid nitrogen or to  $\sim 35$  K using a closed-cycle He refrigerator during the scraping and data acquisition. The cleanliness of the sample surfaces was checked by the absence of extra features at binding energies 9-12 eV and a high-binding energy feature in the O 1s core-level spec-

tra, which arise from contamination or degradation of the sample surfaces. No intrinsic temperature dependence was observed in the spectra although the surfaces were generally very unstable at room temperature.

Figure 1 shows the photoemission spectra of SrVO<sub>3</sub> taken with photon energies in the V 3*p* → 3*d* core absorption region. Above the absorption threshold, *d*-electron emission is enhanced due to the resonance photoemission effect, 3*p*<sup>6</sup>3*d*<sup>*n*</sup> + *hν* → 3*p*<sup>5</sup>3*d*<sup>*n*+1</sup> → 3*p*<sup>6</sup>3*d*<sup>*n*-1</sup> + *e*. Thus the emission within ~3 eV of the Fermi level (*E*<sub>*F*</sub>) is unambiguously identified with the occupied part of the V 3*d* band. Similarly, the Ti 3*d* origin of the emission within ~4 eV of *E*<sub>*F*</sub> for the Ti compounds has been confirmed [8].

One notices in Fig. 1 that the *d* band consists of two structures: One is within ~1 eV of *E*<sub>*F*</sub> with a sharp Fermi cutoff and the other is a broad feature centered ~1.5 eV below *E*<sub>*F*</sub>. Figure 2 shows that, in going from SrVO<sub>3</sub> to LaTiO<sub>3</sub> to YTiO<sub>3</sub>, the ~1.5-eV peak becomes more intense whereas the feature near *E*<sub>*F*</sub> becomes weaker and finally vanishes in the insulating YTiO<sub>3</sub>, for which the 1.5-eV feature is unambiguously assigned to the lower Hubbard (*d*<sup>1</sup> → *d*<sup>0</sup>) band. That is, the relative intensities of the two features show a systematic dependence on *U*<sub>eff</sub>/*W*. In Fig. 2, we also show the spectrum of another *d*<sup>1</sup> system, VO<sub>2</sub> [9], whose *U*<sub>eff</sub>/*W* is expected to be smaller than that of SrVO<sub>3</sub> because *U*<sub>eff</sub> should not be much different among the V<sup>4+</sup> oxides and *W* would be larger in VO<sub>2</sub> due to the much shorter V-V distance [10]. Indeed, in VO<sub>2</sub> the high- and low-binding-energy features

are found to be even weaker and stronger, respectively, than those in SrVO<sub>3</sub> [11].

In Fig. 2, we compare the spectra with the results of nonmagnetic band-structure calculations. The band structures for SrVO<sub>3</sub> and LaTiO<sub>3</sub> have been calculated in the local-density approximation using the augmented-plane-wave (APW) method and the localized-spherical-wave (LSW) method, respectively [12], and that for VO<sub>2</sub> is taken from Ref. [13]. The calculated density of states (DOS) has been appropriately broadened to simulate the instrumental and lifetime broadening effects. The emission within ~1 eV of *E*<sub>*F*</sub> corresponds well to the DOS given by the band-structure calculations. We may therefore assign this feature to itinerant *d*-band states corresponding to the quasiparticle excitations or renormalized *d*-band states and refer to it as the "coherent part" of the spectral function. The high-energy feature is located at energies close to that of the lower Hubbard band of YTiO<sub>3</sub> and has no corresponding feature in the calculated DOS. We therefore attribute this feature to a remnant of the lower Hubbard band and refer to it as the "incoherent part" of the spectral function. In Fig. 2, we also compare the photoemission spectrum of ReO<sub>3</sub> [14] with the band-structure calculation [15]. Because of the extended nature of the Re 5*d* wave functions, *U*<sub>eff</sub>/*W* ≪ 1, and therefore the photoemission spectrum and the calculated DOS are in reasonable agreement without any sign

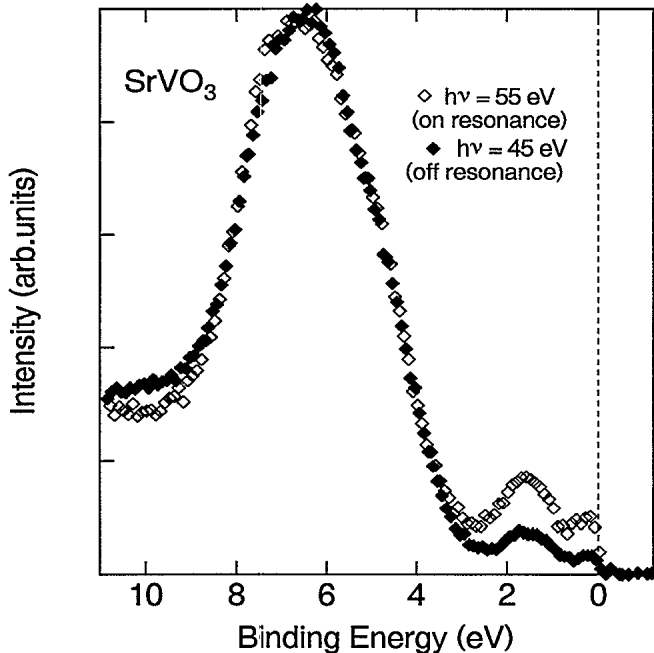


FIG. 1. Photoemission spectra of SrVO<sub>3</sub> for photon energies in the V 3*p* → 3*d* core absorption region. The spectra are normalized at the peak of the O 2*p* band.

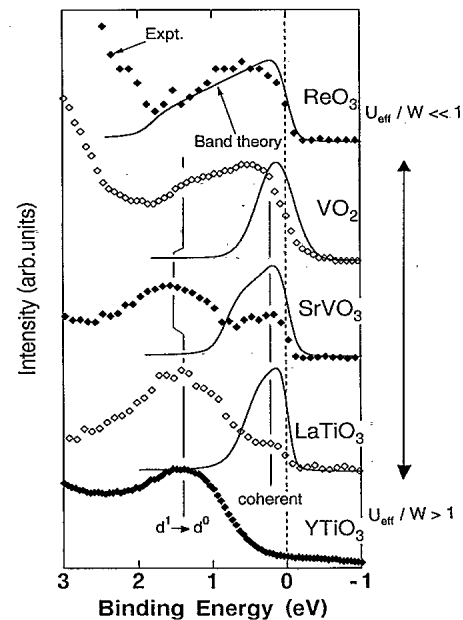


FIG. 2. Photoemission spectra (diamond symbols) of YTiO<sub>3</sub> (*hν* = 21.2 eV), LaTiO<sub>3</sub> (*hν* = 48 eV), and SrVO<sub>3</sub> (*hν* = 55 eV) in the *d*-band region. The spectra of VO<sub>2</sub> in the metallic phase (*hν* = 60 eV) and ReO<sub>3</sub> (*hν* = 40.8 eV) are taken from Refs. [9] and [14], respectively. They are compared with the DOS given by band-structure calculations [13,15] (solid curves). The instrumental resolution is ~0.5 eV for VO<sub>2</sub> and ~0.2–0.3 eV otherwise.

of incoherent spectral weight.

Recently, calculations of the single-particle spectral function have been performed for the single-band Hubbard model at half filling. White *et al.* [16] have performed a Monte Carlo simulation study of the two-dimensional Hubbard model and shown that with decreasing  $U/W$ , the upper and lower Hubbard bands are shifted toward  $E_F$  rather rigidly and coalesce into a single band in the  $U=0$  limit; the transfer of spectral weight from the incoherent to the coherent part is not very clearly demonstrated. Exact diagonalization studies on small clusters have yielded similar results [17]. Menge and Muller-Hartmann [18] have studied the Hubbard model in infinite dimension in a weak-coupling perturbation theory. Their results show that for  $U > 0$ , the band is narrowed near  $E_F$  and that high-energy tails appear, which might correspond to the remnant of the Hubbard bands. Thus the theoretical studies do not necessarily show the persistence of the Hubbard bands in the metallic phase. In order to explain the apparent discrepancy between theory and experiment, effects which have not been taken into account in those theoretical studies, such as the orbital degeneracy of the  $t_{2g}$  band, long-range Coulomb interaction, and electron-phonon interaction, might have to be seriously considered.

We shall then analyze the photoemission data phenomenologically by introducing the *local* self-energy  $\Sigma(\omega)$  of quasiparticles, in which electron correlation and other interaction effects are incorporated. The simplest case where the quasiparticle renormalization factor  $z(\omega) \equiv [1 - \partial \text{Re}\Sigma(\omega)/\partial \omega]^{-1}$  is constant throughout the  $t_{2g}$  band cannot explain the experimental results: With a constant  $z(\omega)$  ( $\equiv z$ ), the  $t_{2g}$  band would be uniformly narrowed by the factor  $z$  and the spectral density at  $E_F$  would remain unchanged, leading to the ratio of the coherent spectral weight to the incoherent one of  $z/(1-z)$ , whereas the photoemission results show that the coherent part is reduced in height rather than in width. The experimental results can be better explained if we allow for the energy dependence of  $z(\omega)$  and assume the form of  $\text{Re}\Sigma(\omega)$  as shown in Fig. 3, where significant band narrowing [ $z(\omega) \ll 1$ ] occurs only in the vicinity of  $E_F$  ( $|\omega| < \omega_0$ ) and  $z(\omega)$  is of order 1 otherwise. The  $\omega_0$  defines the energy scale on which the band narrowing occurs and would decrease with decreasing  $z(\omega \sim 0)$ . As can be seen from Fig. 3, the occupied  $t_{2g}$  band width is then reduced roughly by the amount  $\sim \omega_0/z(0)$  or by a factor  $\sim a \equiv 1 - [\omega_0/z(0)]/W$  and the spectral density near  $E_F$  is also reduced by a similar factor. Thus the coherent to incoherent spectral weight ratio becomes  $\sim a^2/(1-a^2)$ . Using reasonable values  $W \sim 1$  eV,  $1/z(0) \sim 10$ , and  $\omega_0 \sim 0.01-0.05$  eV, we roughly obtain  $a^2/(1-a^2) \sim 0.3-4$ , and the reduction in the occupied  $d$ -band width is only moderate (0.1-0.5 eV), consistent with experiment. Since the spectral density exactly at  $E_F$  should remain unchanged by interaction [19], a narrow peak of the width  $\sim \omega_0$  is predicted at  $E_F$  in the photo-

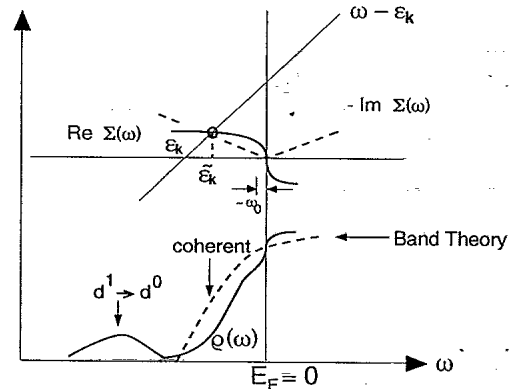


FIG. 3. Proposed energy dependence of the self-energy  $\Sigma(\omega)$  and the spectral function  $\rho(\omega) \equiv -(1/\pi)\text{Im}G(\omega) = -(1/\pi) \times \text{Im}\{1/[\omega - \epsilon_k - \Sigma(\omega)]\}$  in the  $d$ -band region. The noninteracting electron energy  $\epsilon_k$  is shifted by  $\sim \text{Re}\Sigma(\omega)$  to give the quasiparticle energy  $\tilde{\epsilon}_k$ . The  $\rho(\omega)$  of the noninteracting system (dashed curve) is thus modified to give the measured  $\rho(\omega)$  (solid curve).

emission spectra as shown in Fig. 3. The above form of  $\Sigma(\omega)$  is, of course, not a unique solution to explain the photoemission data since the present angle-integrated data with moderate energy resolution do not provide very detailed information. In particular, the detailed form of  $\Sigma(\omega)$  in the vicinity of  $E_F$  should be reflected in low-energy properties such as magnetic susceptibilities and specific heats. High-resolution ( $\ll 0.1$  eV) photoemission studies at low temperatures will be able to answer these questions to some extent.

If we assume the above form of  $\text{Re}\Sigma(\omega)$ , Kramers-Kronig relations predict that  $\text{Im}\Sigma(\omega)$  significantly deviates from the usual Fermi-liquid behavior,  $\sim -\omega^2$ , except for the narrow region  $|\omega| < \omega_0$  and behaves rather like  $\sim -|\omega|$ . A limiting case where  $\omega_0 \rightarrow 0$  and  $z(0) \rightarrow 0$  is referred to as a marginal Fermi liquid [20]. In this case, the interaction is nearly strong enough to make the Fermi liquid unstable and to induce a Mott transition. Indeed, the recent optical study of  $\text{LaTiO}_3$  ( $h\nu > 0.1$  eV) [3] has indicated that the effective mass steeply increases toward  $h\nu \rightarrow 0$  and the relaxation time behaves rather linear in  $h\nu$ .

In conclusion, we have shown how the coherent part of the single-particle spectral function develops around  $E_F$  between the lower and upper Hubbard bands with decreasing  $U_{\text{eff}}/W$ . We point out that such evolution of the spectral function is apparently similar to that of  $4f$  electrons in valence-fluctuating Ce compounds [21] although the underlying model in the latter systems is the impurity Anderson model. The unoccupied part of the spectral functions of the present systems remains to be studied by inverse-photoemission spectroscopy. It is interesting to see how the metallic states produced by the collapse of the Mott-Hubbard gap resemble or differ from those produced by carrier doping [2] and how the situation changes in going from the Mott-Hubbard regime to the

charge-transfer regime. It is also important to obtain a unified picture for the single-particle and two-particle spectral functions, which can be probed by (inverse) photoemission and optical absorption, respectively, because the coherent spectral weight appears considerably enhanced in the latter compared to the former spectral function [22].

We would like to thank T. Mizokawa, K. Yamaguchi, T. Arima, and the staff of the Synchrotron Radiation Laboratory and the Photon Factory for technical support, and M. T. Czyzyk for helping with the LSW calculation. Useful discussions with G. A. Sawatzky, J. C. Fuggle, and Y. Aiura are gratefully acknowledged. This work is supported by a Grant-in-Aid for Scientific Research from the Ministry of Education, Science and Culture of Japan. Part of this work was performed under the approval of the Photon Factory Program Advisory Committee (Proposal No. 91-241).

- [1] J. Hubbard, Proc. R. Soc. London A **276**, 238 (1963); **277**, 237 (1964); **281**, 401 (1964).
- [2] H. Eskes, M. B. J. Meinders, and G. A. Sawatzky, Phys. Rev. Lett. **67**, 1035 (1991).
- [3] J. P. Gopal, J. E. Greedan, and D. A. MacLean, J. Solid State Chem. **43**, 244 (1981).
- [4] F. Lichtenberg, D. Widmer, J. G. Bednorz, T. Williams, and A. Reller, Z. Phys. B **82**, 211 (1991).
- [5] Y. Fujishima, Y. Tokura, T. Arima, and S. Uchida, Physica (Amsterdam) **185-189C**, 1001 (1991); Phys. Rev. B (to be published).
- [6] M. Onoda, H. Ohta, and H. Nagasawa, Solid State Commun. **79**, 281 (1991).
- [7] D. A. MacLean, H.-N. Ng, and J. E. Greedan, J. Solid State Chem. **30**, 35 (1979).
- [8] A. Fujimori, I. Hase, H. Namatame, Y. Fujishima, Y.

- Tokura, M. Nakamura, A. Misu, M. Abbate, F. M. F. de Groot, M. Czyzyk, J. C. Fuggle, O. Strebels, F. Lopez, M. Domke, and G. Kaindl (to be published).
- [9] S. Shin, S. Suga, M. Taniguchi, M. Fujisawa, H. Kanzaki, A. Fujimori, H. Daimon, Y. Ueda, K. Kosuge, and S. Kachi, Phys. Rev. B **41**, 4993 (1990).
- [10] The temperature-dependent metal-insulator transition in VO<sub>2</sub> is a combined effect of electron correlation and a Peierls instability, implying that  $U_{\text{eff}}/W$  might be substantially smaller than 1.
- [11] Photoemission spectra of another "barely metallic" compound CaVO<sub>3</sub> show coherent spectral weight comparable to that of LaTiO<sub>3</sub> and its intensity does not change much with oxygen content [Y. Aiura, F. Iga, Y. Nishihara, and H. Kato (to be published)]. Therefore, the small oxygen off-stoichiometry in the LaTiO<sub>3.03</sub> sample will not affect the present conclusion.
- [12] For simplicity, the crystal structure of LaTiO<sub>3</sub> has been assumed cubic. The structural distortion is not expected to change the density of states significantly and the comparison with the photoemission spectra.
- [13] M. Gupta, D. E. Ellis, and A. J. Freeman, Phys. Rev. B **16**, 3338 (1977).
- [14] A. Fujimori, F. Minami, T. Akahane, and N. Tsuda, J. Phys. Soc. Jpn. **49**, 1820 (1980).
- [15] L. F. Mattheiss, Phys. Rev. **181**, 987 (1969).
- [16] S. R. White, D. J. Scalapino, R. L. Sugar, and N. E. Bickers, Phys. Rev. Lett. **63**, 1523 (1989).
- [17] E. Dagotto, R. Joynt, A. Moreo, S. Bacci, and E. Gagliano, Phys. Rev. B **41**, 9049 (1990); Q. Liu, J. Callaway, and L. Tan, Phys. Rev. B **44**, 10256 (1991).
- [18] B. Menge and E. Muller-Hartmann, Z. Phys. B **82**, 237 (1991).
- [19] A. Khurana, Phys. Rev. B **40**, 4316 (1989).
- [20] C. M. Varma, P. B. Littlewood, and S. Schmitt-Rink, Phys. Rev. Lett. **63**, 1996 (1989).
- [21] O. Gunnarsson and K. Schönhammer, Phys. Rev. B **28**, 4315 (1983).
- [22] S. Uchida, T. Ido, H. Takagi, T. Arima, Y. Tokura, and S. Tajima, Phys. Rev. B **43**, 7942 (1991).